

4. Polymorph of 1,4-diketo-3,6-bis-(4'-dipyridyl)–pyrrolo-[3,4-c]pyrrole and their hydrogen bond network: A material for H₂ gas sensor

Introduction

Diketodiphenylpyrrolopyrroles (for example DPP: Fig. 1(a)) are industrially important organic pigments used not only for paint industries as well as in the imaging areas ¹. DPPs have also attracted attention as a material useful for EL and color filters for LCD applications. The title compound (DPPP: Fig. 1(b)) is a dipyridyl derivative that shows a high proton affinity because of the N atom of the pyridyl ring ². Protonation at the N atom (shown in the inset of Fig. 2) brings about a drastic color change from vivid red to violet, accompanied by changes in electrical conductivity and photoconduction ². For example, the absorption maximum is displaced from 560 to 580 nm due to protonation by vapor of nitric acid as shown in Fig. 2 while the electrical resistivity reduces by several orders of magnitude. The proton affinity is obviously a negative factor for colorants because the color change easily occurs in pigment-dispersed layers due to gradual liberation of protons from the polymer matrix. The proton affinity is, however, a positive factor for applications for H₂ gas sensors. For this reason, we have initiated the investigation for H₂ gas sensors ³. Then, we found that there exist two crystal phases in the solid state of DPPP: one is quite sensitive to protons (phase I: grown from the vapor phase) while the other exhibits a poor proton affinity (phase II: recrystallized from solution). We have successfully isolated these single crystals and analyzed the crystal structure of phases I and II in order to elucidate the correlation between the structure and proton affinity.

Chapter 4 deals with the crystal and electronic structure of phases I and II of DPPP

with special attention to their hydrogen bond network.

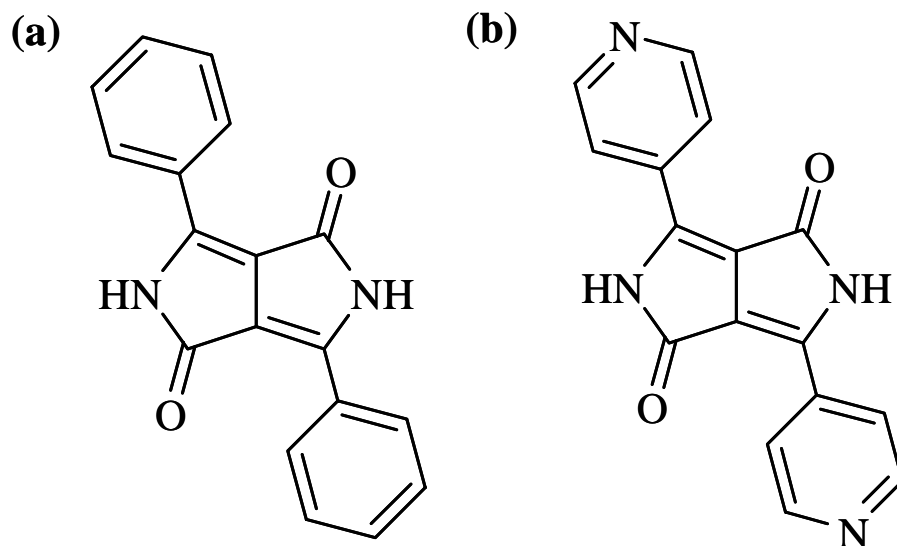


Fig. 1 Molecular conformation: (a) DPP and (b) DPPP.

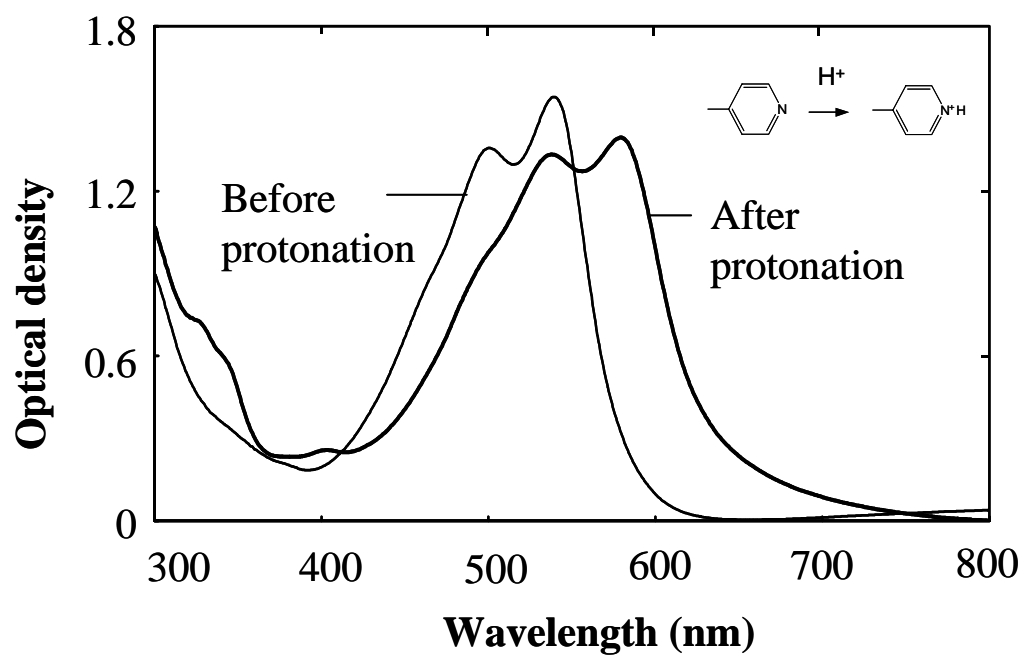


Fig. 2 Solid-state spectra of evaporated DPPP before and after protonation with the vapor of nitric acid.

Experiment

Sample preparation and crystal growth

DPPP was synthesized according to the method described in Ref.4 and purified six times by sublimation, using a two-zone furnace ⁵. Single crystals of phase I were grown from the vapor phase in a closed system based on a two-zone furnace. On the other hand, single crystals of phase II were grown by recrystallization from solution in *N,N*-dimethylacetamide using an autoclave (Taiatsu Co. Ltd.; model TPR-2).

Structure analysis

Reflection data were collected by a R-Axis RAPID-F diffractometer from Rigaku. Structure was solved by direct methods (SHELXS-86) and refinement was carried out by the least-squares method in teXsan program package.

Polarized reflection spectra

Polarized reflection spectra in the visible region were measured on single crystals by means of a microscope-spectrophotometer (UMSP 80 from Carl Zeiss) equipped with an R928 photomultiplier (HTV). Reflectivities were corrected relative to the reflection standard of silicon carbide.

Results and discussion

Crystallographic parameters and molecular conformation of DPPP

Table 1 details the crystallographic parameters for phase I together with those of phase II ⁶. In phase I, the crystal system is monoclinic and the space group is $P2_1/n$. These are two molecules in the unit cell. On the other hand, the space group and molecular symmetry of phase II are $P2_1/c$ and C_1 , respectively. There are four molecules

at the general positions in the unit cell.

Table 1
Crystallographic parameters for phases I and II of DPPP

	Phase I	Phase II
Crystal system	monoclinic	monoclinic
Space group	$P2_1/n$	$P2_1/c$
Molecular symmetry	C_i	C_1
Z	2	4
a (Å)	3.722(1)	3.695(1)
b (Å)	6.263(3)	18.201(2)
c (Å)	26.506(9)	18.456(2)
β (°)	94.41(2)	94.68(1)
V (Å ³)	616.0(4)	1237.1(3)

Figs. 3(a) and 3(b) show the ORTEP plots of phases I and II, respectively. Because of the C_i symmetry in phase I, the pyridyl rings are twisted in the same direction by about 6.5° with respect to the heterocyclic ring. In phase II, the two pyridyl rings are asymmetrically twisted in opposite directions by 4.2° and 15.3°.

Molecular arrangement and intermolecular hydrogen bonds

Figs. 4(a) and 4(b) shows the projection of the crystal structure of phase I onto the (b,c) and (a,c) planes, respectively. The dotted lines represent the intermolecular hydrogen bonds between the NH group of one molecule and the O atom of the neighboring one (N/O distance: 2.85 Å). There are chains of NH...O H-bonds along the b -axis. This type of two-dimensional H-bond network is found in common in all DPP

pigments. The molecules are arranged in a zigzag fashion along the *c*-axis and stacked along the *a*-axis. It is also to be noted that two N atoms in each pyridyl ring remain free and can accept protons. For this reason, phase I is ideal for applications of H₂ gas sensors.


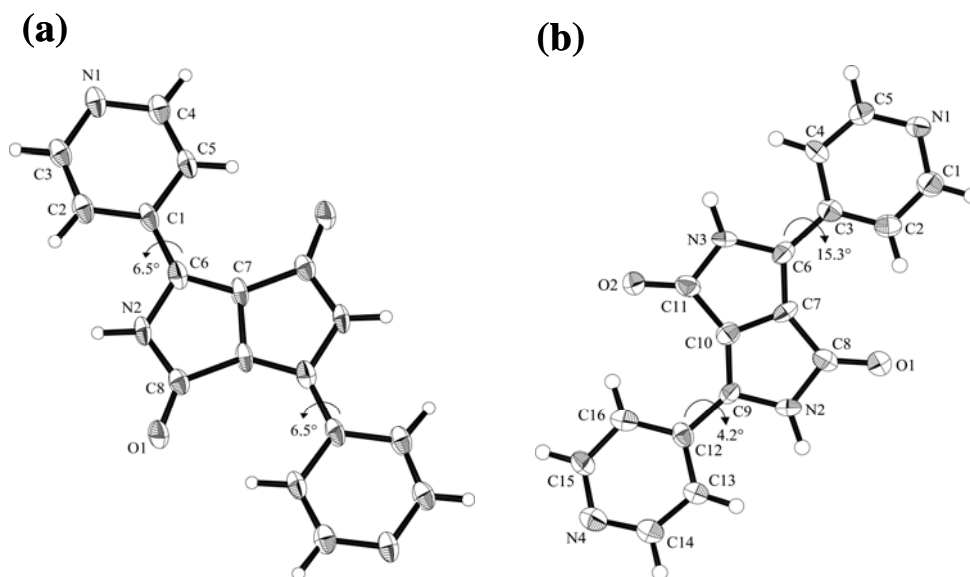


Fig. 3 ORTEP plots: (a) phase I and (b) phase II.

On the other hand, the H-bond fashion and H-bond network are quite different in phase II. The projection of the crystal structure onto the (*b*,*c*) and (*a*,*c*) planes is shown in Figs. 5(a) and 5(b), respectively. On the (*b*,*c*) plane, there are two types of the H-bond. One is the NH...O between the NH group of one molecule and the O atom of the neighboring one (N/O distance: 2.84 Å). The other is based on the NH...N between the NH group of one molecule and the N atom of the pyridyl ring of the neighboring molecule (N/N distance: 2.89 Å). In each molecule, there are two H-bonds of the NH...O type as well as two bonds of the NH...N type. In addition, there remains one free N atom. The molecule-pairs which sit side by side through NH...O hydrogen bonds behave

(a)

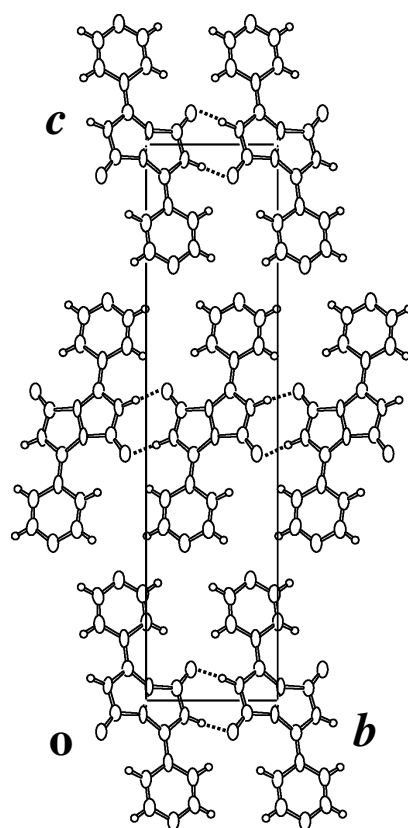

(b)


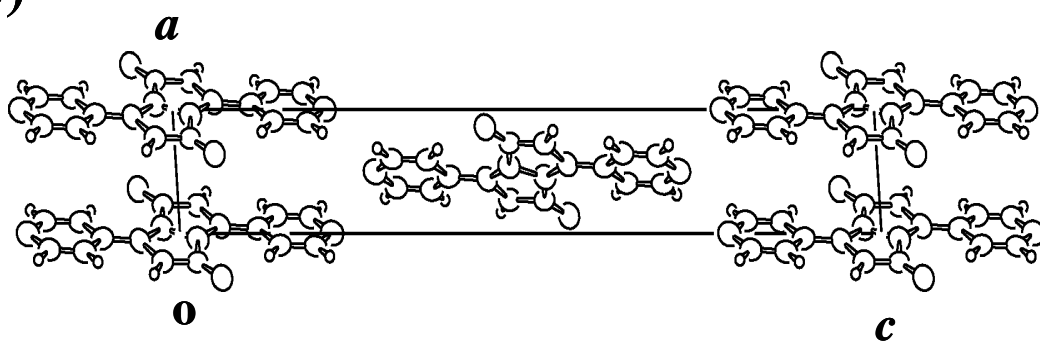


Fig. 4 Projection of phase I onto: (a) (b,c) plane and (b) (a,c) plane.

(a)

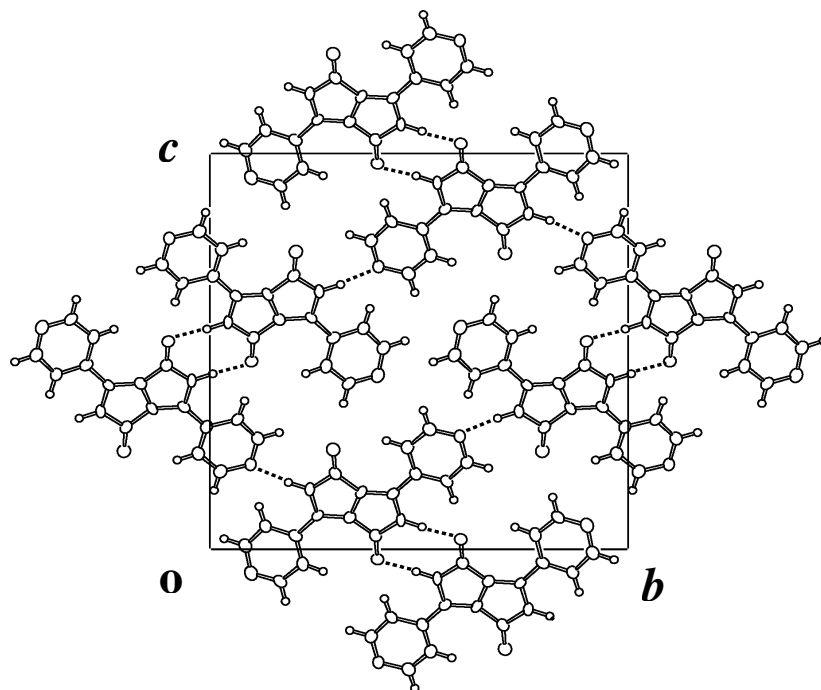

(b)

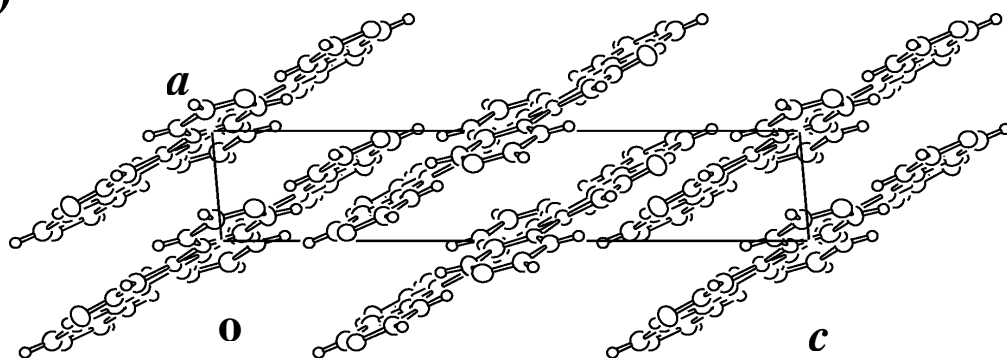


Fig. 5 Projection of phase II onto: (a) (b, c) plane and (b) (a, c) plane.

as the repeating unit in the crystal lattice and are arranged in a zigzag fashion along the *b*-axis as well as the *c*-axis on the molecular plane. There is also a local H-bond ring network composed of six molecules: four NH \cdots N and two bifurcated NH \cdots O bonds. The present two-dimensional H-bond network is quite unique of phase II, not found in ordinary DPPs. The molecules are stacked along the *a*-axis. It should be also noted that in phase II, one N atom is used for the formation of NH \cdots N hydrogen bond while the other remains free. Therefore phase II is less sensitive to protons as compared with phase I. For this reason, phase II is appropriate for colorant applications because the color change caused by protonation is significantly suppressed.


Polarized reflection spectra measured on single crystals

Figs. 6(a) and 6(b) show the polarized reflection spectra of phase I measured on the (*b,c*) plane of single crystals and the corresponding projection, respectively. The direction of the transition dipole as deduced from MO calculations is depicted in dotted lines in Fig. 6(b). Polarized light was introduced in parallel or perpendicular to the *b*-axis. A prominent reflection band appears around 550 nm together with a reflection shoulder around 450 nm for polarization parallel to *b*-axis. On the other hand, these intense reflection bands completely disappear for polarization perpendicular to the *b*-axis. This indicates that the transition dipole points along the *b*-axis which is the direction of the NH \cdots O intermolecular H-bonds. The direction of the transition dipole as determined by experiment is in good agreement with that predicted by MO calculations.

Figs. 7(a) and 7(b) show the polarized reflection spectra of phase II measured on the (*a,c*) plane of single crystals and its corresponding projection, respectively. Measurements were made with polarized light along or perpendicular to the molecular plane. A strong reflection band appear around 450 nm together with small bands

peaking around 480 and 540 nm for polarization along the molecular plane. These bands are, however, completely quenched for polarization perpendicular to the molecular plane.

(a)

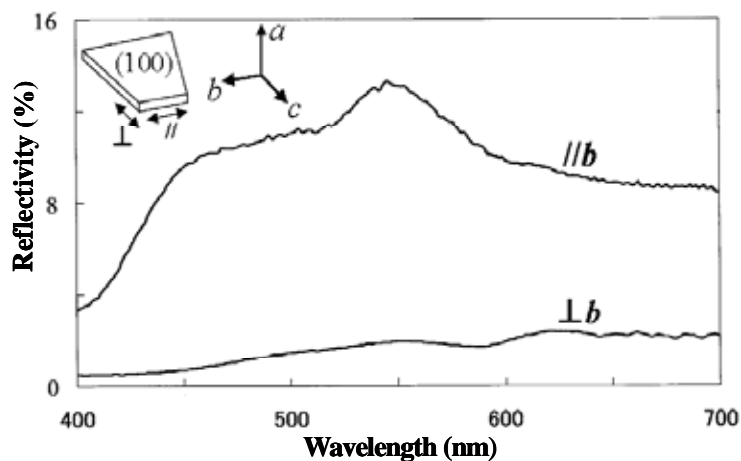

(b)


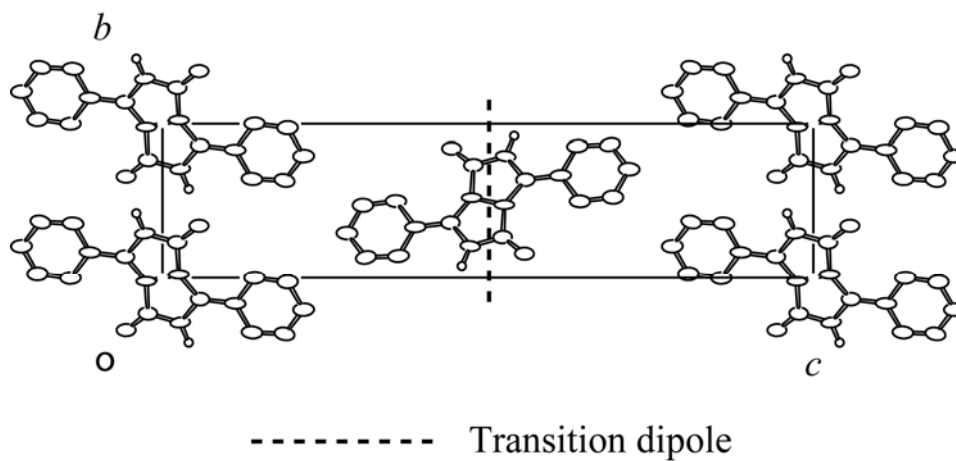


Fig. 6 (a) Polarized reflection spectra of phase I measured on the (100) plane of single crystals and (b) projection of phase I onto the (b,c) plane.

(a)

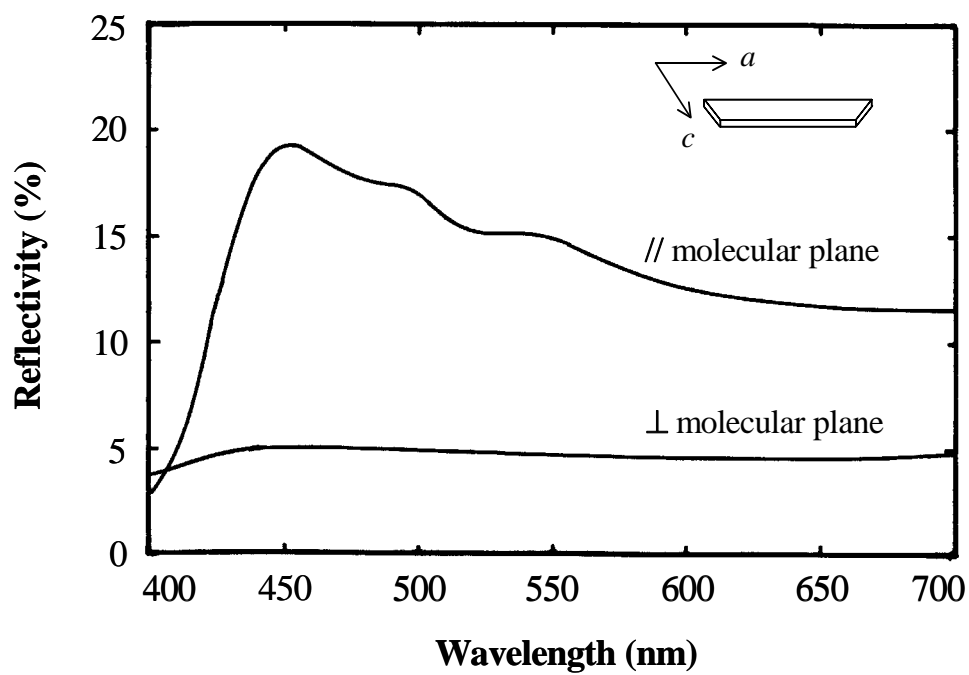

(b)

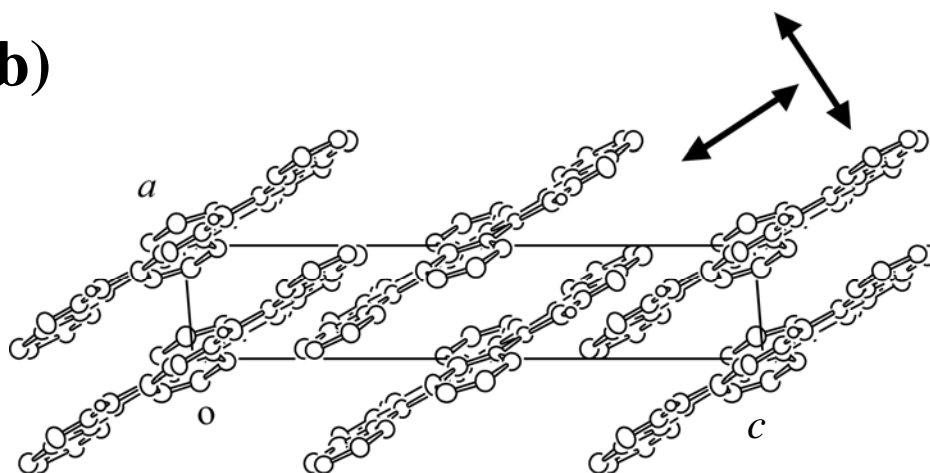


Fig. 7 (a) Polarized reflection spectra of phase II measured on the (010) plane of single crystals and (b) projection of phase II onto the (*a,c*) plane.

As seen from the above results, it is remarkable to note that the reflection spectra for phases I and II are strikingly different, depending on the molecular arrangement governed by the fashion of the $\text{NH}\cdots\text{O}$ and/or $\text{NH}\cdots\text{N}$ hydrogen bond network. This is mainly due to excitonic interactions as discussed previously for a variety of DPP derivatives⁷.

Conclusions

Structural characterization has been carried out on phases I and II in an attempt to clarify the correlation between the structure and proton affinity. The conclusions can be summarized as follows.

1. Phase I crystallizes in space group of $P2_1/n$ with $Z = 2$. There are four $\text{NH}\cdots\text{O}$ hydrogen bonds per molecule as found in ordinary DPPs. The N atom of the pyridyl ring remains free and thus can easily accept protons. Therefore, phase I is ideal for applications of H_2 gas sensors. The transition dipole of phase I points along the $\text{NH}\cdots\text{O}$ intermolecular hydrogen bond.
2. In phase II, the space group is $P2_1/c$ with $Z = 4$ and there are two types of hydrogen bonds: $\text{NH}\cdots\text{O}$ and $\text{NH}\cdots\text{N}$. The $\text{NH}\cdots\text{N}$ hydrogen bond is formed between the NH group of one molecule and the N atom of the pyridyl ring of the neighboring molecule. Then, one of the two N atoms of the pyridyl rings is protected by the $\text{NH}\cdots\text{N}$ hydrogen bond while the other is free. Therefore, phase II is rather resistant to color change due to protonation.

References

1. M. Herbst and K. Hunger, *Industrial Organic Pigments*, VCH, Weinheim, (1993).
2. J. Mizuguchi, *Ber Bunsenges Phys. Chem.*, **97**, 684 (1993).
3. H. Takahashi and J. Mizuguchi, *J. Electrochem. Soc.*, **152**, H69-H73 (2005).
4. A. C Rochat, L. Cassar and A. Iqbal, U.S. Pat. 4, 579, 949 (1986).
5. J. Mizuguchi, *Krit. Tech.*, **16**, 695 (1981).
6. J. Mizuguchi, H. Takahashi and H. Yamakami, *Z. Kristallogr. NCS*, **217**, 519 (2002).
7. J. Mizuguchi, *J. Phys. Chem. A.*, **104**, 1817 (2002).